

PROPERTIES OF SUPERCONDUCTORS

L. I. Berger and B. W. Roberts

The following tables include superconductive properties of selected elements, compounds, and alloys. Individual tables are given for thin films, elements at high pressures, superconductors with high critical magnetic fields, and high critical temperature superconductors.

The historically first observed and most distinctive property of a superconductive body is the near total loss of resistance at a critical temperature (T_c) that is characteristic of each material. Figure 1(a) below illustrates schematically two types of possible transitions. The sharp vertical discontinuity in resistance is indica-

tive of that found for a single crystal of a very pure element or one of a few well annealed alloy compositions. The broad transition, illustrated by broken lines, suggests the transition shape seen for materials that are not homogeneous and contain unusual strain distributions. Careful testing of the resistivity limit for superconductors shows that it is less than 4×10^{-23} ohm cm, while the lowest resistivity observed in metals is of the order of 10^{-13} ohm cm. If one compares the resistivity of a superconductive body to that of copper at room temperature, the superconductive body is at least 10^{17} times less resistive.

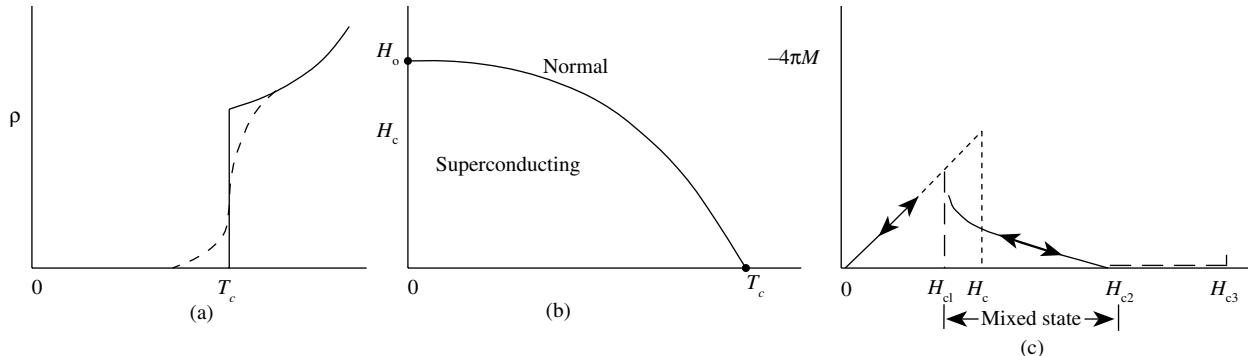


FIGURE 1. Physical properties of superconductors. (a) Resistivity vs. temperature for a pure and perfect lattice (solid line); impure and/or imperfect lattice (broken line). (b) Magnetic-field temperature dependence for Type-I or "soft" superconductors. (c) Schematic magnetization curve for "hard" or Type-II superconductors.

The temperature interval ΔT_c , over which the transition between the normal and superconductive states takes place, may be of the order of as little as 2×10^{-5} K or several K in width, depending on the material state. The narrow transition width was attained in 99.9999% pure gallium single crystals.

A Type-I superconductor below T_c , as exemplified by a pure metal, exhibits perfect diamagnetism and excludes a magnetic field up to some critical field H_c , whereupon it reverts to the normal state as shown in the H - T diagram of Figure 1(b).

The magnetization of a typical high-field superconductor is shown in Figure 1(c). The discovery of the large current-carrying capability of Nb_3Sn and other similar alloys has led to an extensive study of the physical properties of these alloys. In brief, a high-field superconductor, or Type-II superconductor, passes from the perfect diamagnetic state at low magnetic fields to a mixed state and finally to a sheathed state before attaining the normal resistive state of the metal. The magnetic field values separating the four stages are given as H_{c1} , H_{c2} , and H_{c3} . The superconductive state below H_{c1} is perfectly diamagnetic, identical to the state of most pure metals of the "soft" or Type-I superconductor. Between H_{c1} and H_{c2} a "mixed superconductive state" is found in which fluxons (a minimal unit of magnetic flux) create lines of normal flux in a superconductive matrix. The volume of the normal state is proportional to $-4\pi M$ in the "mixed state" region. Thus at H_{c2} the fluxon density has become so great as to drive the interior volume of the superconductive body completely normal. Between H_{c2} and H_{c3} the superconductor has a sheath of current-carrying superconductive material at the body surface, and above H_{c3} the normal state exists. With several types of careful measurement, it is possible to determine H_{c1} , H_{c2} , and H_{c3} . Table 6 contains some of the available data on high-field superconductive materials.

High-field superconductive phenomena are also related to specimen dimension and configuration. For example, the Type-I superconductor, Hg, has entirely different magnetization behavior in high magnetic fields when contained in the very fine sets of filamentary tunnels found in an unprocessed Vycor glass. The great majority of superconductive materials are Type-II. The elements in very pure form and a very few precisely stoichiometric and well annealed compounds are Type I with the possible exceptions of vanadium and niobium.

Metallurgical Aspects. The sensitivity of superconductive properties to the material state is most pronounced and has been used in a reverse sense to study and specify the detailed state of alloys. The mechanical state, the homogeneity, and the presence of impurity atoms and other electron-scattering centers are all capable of controlling the critical temperature and the current-carrying capabilities in high-magnetic fields. Well annealed specimens tend to show sharper transitions than those that are strained or inhomogeneous. This sensitivity to mechanical state underlines a general problem in the tabulation of properties for superconductive materials. The occasional divergent values of the critical temperature and of the critical fields quoted for a Type-II superconductor may lie in the variation in sample preparation. Critical temperatures of materials studied early in the history of superconductivity must be evaluated in light of the probable metallurgical state of the material, as well as the availability of less pure starting elements. It has been noted that recent work has given extended consideration to the metallurgical aspects of sample preparation.

Symbols in tables: T_c : Critical temperature; H_c : Critical magnetic field in the $T = 0$ limit; θ_D : Debye temperature; and γ : Electronic specific heat.

TABLE 1. Selective Properties of Superconductive Elements

Element	T_c (K)	H_o (oersted)	θ_D (K)	γ (mJ mol ⁻¹ K ⁻¹)
Al	1.175 ± 0.002	104.9 ± 0.3	420	1.35
Am* ($\alpha, ?$)	0.6			
Am* ($\beta, ?$)	1.0			
Be	0.026			0.21
Cd	0.517 ± 0.002	28 ± 1	209	0.69
Ga	1.083 ± 0.001	58.3 ± 0.2	325	0.60
Ga (β)	5.9, 6.2	560		
Ga (γ)	7	950, HF ^a		
Ga (Δ)	7.85	815, HF		
Hf	0.128	12.7		2.21
Hg (α)	4.154 ± 0.001	411 ± 2	87, 71.9	1.81
Hg (β)	3.949	339	93	1.37
In	3.408 ± 0.001	281.5 ± 2	109	1.672
Ir	0.1125 ± 0.001	16 ± 0.05	425	3.19
La (α)	4.88 ± 0.02	800 ± 10	151	9.8
La (β)	6.00 ± 0.1	1096, 1600	139	11.3
Lu	0.1 ± 0.03	350 ± 50		
Mo	0.915 ± 0.005	96 ± 3	460	1.83
Nb	9.25 ± 0.02	2060 ± 50, HF	276	7.80
Os	0.66 ± 0.03	70	500	2.35
Pa	1.4			
Pb	7.196 ± 0.006	803 ± 1	96	3.1
Re	1.697 ± 0.006	200 ± 5	4.5	2.35
Ru	0.49 ± 0.015	69 ± 2	580	2.8
Sn	3.722 ± 0.001	305 ± 2	195	1.78
Ta	4.47 ± 0.04	829 ± 6	258	6.15
Tc	7.8 ± 0.1	1410, HF	411	6.28
Th	1.38 ± 0.02	1.60 ± 3	165	4.32
Ti	0.40 ± 0.04	56	415	3.3
Tl	2.38 ± 0.02	178 ± 2	78.5	1.47
U	0.2			
V	5.40 ± 0.05	1408	383	9.82
W	0.0154 ± 0.0005	1.15 ± 0.03	383	0.90
Zn	0.85 ± 0.01	54 ± 0.3	310	0.66
Zr	0.61 ± 0.15	47	290	2.77
Zr (ω)	0.65, 0.95			

TABLE 2. Range of Critical Temperatures Observed for Superconductive Elements in Thin Films Condensed Usually at Low Temperatures

Element	T_c Range (K)	Comments	Element	T_c Range (K)	Comments
Al	1.15–5.7	HF ^a	Nb	2.0–10.1	
Be	5–9.75	HF	Pb	1.8–7.5	
Bi	6.17–6.6		Re	1.7–7	
Cd			Sn	3.5–6	
(Disordered)	0.79–0.91		Ta	<1.7–4.51	HF ^a
(Ordered)	0.53–0.59		Tc	4.6–7.7	
Ga	2.5–8.5	HF	Ti	1.3 Max	
Hg	3.87–4.5		Tl	2.33–2.96	
In	2.2–5.6	HF	V	1.8–6.02	
La	3.55–6.74		W	<1.0–4.1	
Mo	3.3–8.0		Zn	0.77–1.9	

^a HF denotes high magnetic field superconductive properties.

TABLE 3. Elements Exhibiting Superconductivity Under or After Application of High Pressure

Element	T_c Range (K)	Pressure (kbar)	Element	T_c Range (K)	Pressure (kbar)
Al	1.98–0.075	0–62	Pb II	3.55	160
As	0.31–0.5	220–140	Re II	2.3 Max.	"Plastic" compression
	0.2–0.25	140–100	Sb (prepared 120 kbar, held below 77K)	2.6–2.7	
Ba II	1–1.8	55–85	Sb II	3.55–3.40	85–150
III	1.8–5	85–144	Se II	6.75, 6.95	130
IV	4.5–5.4	144–190	Si	6.7–7.1	120–130
Bi II	3.9	25–27	Sn II	5.2–4.85	125–160
III	6.55–7.25	28–38	III	5.30	113
IV	7.0, 8.7–6.0	43, 43–62	Te II	2.4–5.1	38–55
V	6.7, 8.3	48–80	IV	4.1–4.2	53–62
VI	8.55	90, 92–101	()	4.72–4	63–80
VII(?)	8.2	30	Tl (cubic form)	3.3–2.8	100–260
Ce (α)	0.020–0.045	20–35	(hexagonal form)	1.45	35
Ce (α')	1.9–1.3	45–125	U	1.95	35
Cs V	1.5	>125	Y	2.4–0.4	10–85
Ga II	6.38	\geq 35	Zr (omega form, metastable)	1.7–2.5	110–160
II'	7.5	\geq 35 then P removed		1–1.7	60–130
Ge	5.35	115			
Lu	0.022–1.0	45–190			
P	5.8	170			

TABLE 4. Superconductive Compounds and Alloys

All compositions are denoted on an atomic basis, i.e., AB, AB₂, or AB₃ for compounds, unless noted. Solid solutions or odd compositions may be denoted as A_zB_{1-z} or A_zB. A series of three or more alloys is indicated as A_xB_{1-x} or by actual indication of the atomic fraction range, such as A_{0.6}–_{0.4}B_{1-0.4}. The critical temperature of such a series of alloys is denoted by a range of values or possibly the maximum value.

The selection of the critical temperature from a transition in the effective permeability, or the change in resistance, or possibly the incremental changes in frequency observed by certain techniques is not often obvious from the literature. Most authors choose the

mid-point of such curves as the probable critical temperature of the idealized material, while others will choose the highest temperature at which a deviation from the normal state property is observed. In view of the previous discussion concerning the variability of the superconductive properties as a function of purity and other metallurgical aspects, it is recommended that appropriate literature be checked to determine the most probable critical temperature or critical field of a given alloy.

A very limited amount of data on critical fields, H_o , is available for these compounds and alloys; these values are given at the end of the table.

A. Superconductors with $T_c < 10$ K

Substance	T_c , K	Crystal structure type	Substance	T_c , K	Crystal structure type
Ag _{3.3} Al	0.34	A12-cl58 (Mn)	Ag _x NO ₁₁	1.04	Cubic
Ag _x Al _y Zn _{1-x-y}	0.15	Cubic	Ag _x Pb _{1-x}	7.2 max.	
AgBi ₂	2.87–3.0		Ag _x Sn	0.1	h**
Ag _{0.25} F _{0.75} N _{0.1025} O _{10.25}	0.85–0.90		Ag _x Sn _{1-x}	1.5–3.7	
Ag ₂ F	0.0066		Ag _x Sn _{1-x} (film)	2.0–3.8	
Ag ₇ FO ₈	0.3	Cubic	AgTe ₃	2.6	Cubic
Ag _{0.8} – _{0.3} Ga _{0.2} – _{0.7}	6.5–8		AgTh	2.2	C16-tl12 (Al ₂ Cu)
Ag ₄ Ge	0.85	Hex., c.p.	AgTh ₂	2.26	C16
Ag _{0.438} Hg _{0.562}	0.64	D8 ₂	Ag _{0.03} Tl _{0.97}	2.67	
AgIn ₂	~2.4	C16	Ag _{0.94} Tl _{0.06}	2.32	
Ag _{0.1} In _{0.9} Te (n = 1.4 × 10 ²²)*	1.2–1.89	B1	AgY	0.33	B2-cP2 (CsCl)
Ag _{0.2} In _{0.8} Te (n = 1.07 × 10 ²²)	0.77–1.00	B1	Ag _x Zn _{1-x}	0.5–0.845	
AgLa	0.94	B2-cP2 (CsCl)	AlAu ₄	0.4–0.7	Like A13
AgLa (9.5 kbar)	1.2	B2	Al ₂ Au	0.1	C1-cF12 (CaF ₂)
AgLu	0.33	B2-cP2	Al ₂ CMo ₃	9.8–10.2	A13+trace 2nd. phase
AgMo ₄ S ₅	9.1	hR15 (Mo ₆ PbS ₈)	Al ₂ CaSi	5.8	
Ag _{1.2} Mo ₆ Se ₈	5.9	Same	Al _{0.131} Cr _{0.088} V _{0.781}	1.46	Cubic
			AlGe ₂	1.75	

Substance	T_c , K	Crystal structure type	Substance	T_c , K	Crystal structure type
$\text{Al}_2\text{Ge}_2\text{U}$	1.6	$\text{LI}_{2-\text{x}}\text{P4}$ (Cu_3Au)	AuPb_2	3.15	
AlLi_3	5.57	DO_{19}	AuPb_2 (film)	4.3	
Al_2La	3.23	C15	AuPb_3	4.40	
Al_2Lu	1.02	C15-cF24 (Cu_2Mg)	AuPb_3 (film)	4.25	
Al_3Mg_2	0.84	F.C.C.	Au_2Pb	1.18; 6–7	C15
AlMo_3	0.58	A15	AuSb_2	0.58	C2
AlMo_6Pd	2.1		AuSn	1.25	$\text{B}8_1$
AlN	1.55	B4	$\text{Au}_{x}\text{Sn}_{1-x}$ (film)	2.0–3.8	
Al_2NNb_3	1.3	A13	Au_5Sn	0.7–1.1	A3
Al_3Nb	0.64	tI8 (Al_3Ti)	$\text{AuTa}_{4.3}$	0.55	A15-cP8 (Cr_3Si)
AlOs	0.39	B2	Au_3Te_5	1.62	Cubic
Al_3Os	5.90		AuTh_2	3.08	C16
AlPb (film)	1.2–7		AuTl	1.92	
Al_2Pt	0.48–0.55	C1	AuV_3	0.74	A15
$\text{Al}_5\text{Re}_{24}$	3.35	A12	$\text{Au}_{x}\text{Zn}_{1-x}$	0.50–0.845	
AlSb	2.8	B4-tI4 (Sn)	AuZn_3	1.21	Cubic
Al_2Sc	1.02	C15-cF24 (Cu_2Mg)	$\text{Au}_{\text{y}}\text{Zr}_{\text{y}}$	1.7–2.8	A3
$\text{Al}_2\text{Si}_2\text{U}$	1.34	$\text{LI}_{2-\text{x}}\text{P4}$ (Cu_3Au)	AuZr_3	0.92	A15
AlTh_2	0.1	C16-tI12 (Al_2Cu)	$\text{B}_3\text{Ba}_{0.67}\text{Pt}_3$	5.60	hP12 (B_2BaPt_3)
Al_3Th	0.75	DO_{19}	BCMo_2	5.4	Orthorhombic
$\text{Al}_x\text{Ti}_y\text{V}_{1-x-y}$	2.05–3.62	Cubic	BCMo_2	5.3–7.0	Same
$\text{Al}_{0.108}\text{V}_{0.892}$	1.82	Cubic	$\text{B}_2\text{Ca}_{0.67}\text{Pt}_3$	1.57	hP12
Al_2Y	0.35	C15-cF24 (Cu_2Mg)	B_4ErIr_4	2.1	tP18 (B_4CeCo_4)
Al_3Yb	0.94	$\text{LI}_{2-\text{x}}\text{P4}$ (Cu_3Au)	B_4ErRh_4	4.3	oC108 (B_4LuRh_4)
$\text{Al}_x\text{Zn}_{1-x}$	0.5–0.845		B_4ErRh_4	8.7	tP18 (B_4CeCo_4)
AlZr_3	0.73	L1 ₂	BHf	3.1	Cubic
AsBiPb	9.0		B_4HoIr_4	2.0	tP18
AsBiPbSb	9.0		B_4HoRh_4	1.4	oC108
AsHfOs	3.2	C22-hP9 (Fe_2P)	$\text{B}_2\text{Ir}_3\text{La}$	1.65	hP6 (CaCu_5)
AsHfRu	4.9	same	$\text{B}_2\text{Ir}_3\text{Th}$	2.09	Same
$\text{As}_{0.33}\text{InTe}_{0.67}$ ($n = 1.24 \times 10^{22}$)	0.85–1.15	B1	$\text{B}_4\text{Ir}_4\text{Tm}$	1.6	tP18
$\text{As}_{0.5}\text{InTe}_{0.5}$ ($n = 0.97 \times 10^{22}$)	0.44–0.62	B1	B_6La	5.7	
As_4La_3	0.6	cI28 (Th_3P_4)	B_2LaRh_3	2.82	hP6
AsNb_3	0.3	L1 ₂ -tP32	B_{12}Lu	0.48	
$\text{As}_{0.50}\text{Ni}_{0.06}\text{Pd}_{0.44}$	1.39	C2	B_2LuOs	2.66	oP16 (B_2LuRu)
$\text{AsNi}_{0.25}\text{Pd}_{0.75}$	1.6	$\text{B}8_1$ -hP4 (NiAs)	B_2LuOs_3	4.62	hP6
AsOsZr	8.0	C22-hP9 (Fe_2P)	B_4LuRh_4	6.2	oC108
AsPb	8.4		B_2LuRu	9.86	oP16
AsPd_2 (low-temp. phase)	0.60	Hexagonal	B_4LuRu_4	2.0	tI72 (B_4LuRu_4)
AsPd_2 (high-temp. phase)	1.70	C22	BMo	0.5	(extrapol.)
AsPd_5	0.46	Complex	BMo_2	4.74	C16
As_3Pd_5	1.9		BNb	8.25	B_f
AsRh	0.58	B31	B_4NdRh_4	5.3	tP18
$\text{AsRh}_{1.4-1.6}$	< 0.03–0.56	Hexagonal	B_2OsSc	1.34	oP16
AsSn	4.10		B_2OsY	2.22	oP16
AsSn ($n = 2.14 \times 10^{22}$)	3.41–3.65	B1	$\text{B}_2\text{Pt}_3\text{Sr}_{0.67}$	2.78	hP12 (B_2BaPt_3)
$\text{As}_{2-\text{x}}\text{Sn}_{\text{x}}$	1.21–1.17		BRe_2	2.80; 4.6	
As_3Sn_4 ($n = 0.56 \times 10^{22}$)	1.16–1.19	Rhombohedral	$\text{B}_4\text{Rh}_{3.4}\text{Ru}_{0.6}$	8.38	tI72
AsV_3	0.20	A15-cP8 (Cr_3Si)	$\text{B}_4\text{Rh}_4\text{Sm}$	2.7	tP18
Au_5Ba	0.4–0.7	D2 _d	$\text{B}_4\text{Rh}_4\text{Th}$	4.3	Same
AuBe	2.64	B20	$\text{B}_4\text{Rh}_4\text{Tm}$	9.8	Same
Au_2Bi	1.80	C15	$\text{B}_4\text{Rh}_4\text{Tm}$	5.4	oC108
Au_5Ca	0.34–0.38	C15 _b	$\text{B}_{0.3}\text{Ru}_{0.7}$	2.58	$\text{D}10_2$
AuGa_2	1.6	C1-cF12 (CaF_2)	$\text{B}_2\text{Ru}_4\text{Sc}$	7.2	tI72
AuGa	1.2	B31	$\text{B}_2\text{Ru}_3\text{Th}$	1.79	hP6
$\text{Au}_{0.40-0.92}\text{Ge}_{0.60-0.08}$	<0.32–1.63	Complex	$\text{B}_2\text{Ru}_3\text{Y}$	2.85	Same
AuIn_2	0.2	C1-cF12	$\text{B}_2\text{Ru}_3\text{Y}$	7.80	oP16
AuIn	0.4–0.6	Complex	$\text{B}_4\text{Ru}_4\text{Y}$	1.4	tI72
AuLu	<0.35	B2	B_{12}Sc	0.39	
AuNb_3	1.2	A2	BTa	4.0	B_f

Substance	T_c , K	Crystal structure type	Substance	T_c , K	Crystal structure type
BTa ₂	3.12	C16-tI12 (Al ₂ Cu)	Bi ₂ Pd	1.70	Monoclinic, α -phase
B ₆ Th	0.74		Bi ₂ Pd	4.25	Tetragonal, β -phase
BW ₂	3.1	C16	BiPd _{0.45} Pt _{0.55}	3.7	B8 ₁ -hP4 (NiAs)
B ₆ Y	6.5–7.1		BiPdSe	1.0	C2
B ₁₂ Y	4.7		BiPdTe	1.2	C2
BZr	3.4	Cubic	BiPt	1.21	B8 ₁
B ₁₂ Zr	5.82		Bi _{0.1} PtSb _{0.9}	2.05; 1.5	B8 ₁ -hP4 (NiAs)
BaBi ₃	5.69	Tetragonal	BiPtSe	1.45	C2
Ba ₂ Mo ₁₅ Se ₁₉	2.75	hP15 (Mo ₆ PbS ₈)	BiPtTe	1.15	C2
Ba _x O ₃ Sr _{1-x} Ti (n = 4.2 × 10 ¹⁹)	<0.1–0.55		Bi ₂ Pt	0.155	Hexagonal
Ba _{0.13} O ₃ W	1.9	Tetragonal	Bi ₂ Rb	4.25	C15
Ba _{0.14} O ₃ W	<1.25–2.2	Hexagonal	BiRe ₂	1.9–2.2	
BaRh ₂	6.0	C15	BiRh	2.06	B8 ₁
Be ₂₂ Mo	2.51	Cubic (Be ₂₂ Re)	Bi ₃ Rh	3.2	Orthorhombic (NiB ₃)
Be ₈ Nb ₅ Zr ₂	5.2		Bi ₄ Rh	2.7	Hexagonal
Be _{0.98–0.92} Re _{0.02–0.08} (quenched)	9.5–9.75	Cubic	BiRu	5.7	m**
Be _{0.957} Re _{0.043}	9.62	Cubic (Be ₂₂ Re)	Bi ₃ Sn	3.6–3.8	
BeTc	5.21	Cubic	BiSn	3.8	
Be ₂₂ W	4.12	Cubic (Be ₂₂ Re)	Bi _x Sn _y	3.85–4.18	
Be ₁₃ W	4.1	Tetragonal	Bi ₂ Sr	5.62	L1 ₂
Bi ₃ Ca	2.0		Bi ₃ Te	0.75–1.0	
Bi _{0.5} Cd _{0.13} Pb _{0.25} Sn _{0.12} (weight fractions)	8.2		Bi ₅ Tl ₃	6.4	
BiCo	0.42–0.49		Bi _{0.26} Tl _{0.74}	4.4	Cubic, disordered
Bi ₂ Cs	4.75	C15	Bi ₂ Y ₃	4.15	L1 ₂ , ordered (?)
Bi _x Cu _{1-x} (electrodeposited)	2.2		Bi ₃ Zn	2.25	
BiCu	1.33–1.40		Bi _{0.3} Zr _{0.7}	0.8–0.9	
Bi ₃ Fe	1.0	m**	Bi ₃ Zr ₃	1.51	
Bi _{0.019} In _{0.981}	3.86		BrMo ₆ Se ₇	2.4–2.8	
Bi _{0.05} In _{0.95}	4.65	α -phase	Br ₃ Mo ₆ Se ₅	7.1	hP15 (Mo ₆ PbS ₈)
Bi _{0.10} In _{0.90}	5.05	Same	CCs _x	7.1	Same
Bi _{0.15–0.30} In _{0.85–0.70}	5.3–5.4	α - and β -phases	CCs _x	0.020–0.135	Hexagonal
Bi _{0.34–0.48} In _{0.66–0.52}	4.0–4.1		CFe ₃	1.30	DO ₁₁ -oP16 (Fe ₃ C)
Bi ₃ In ₅	4.1		CGaMo ₂	3.7–4.1	Hexagonal
BiIn ₂	5.65	β -phase	CHf _{0.5} Mo _{0.5}	3.4	B1
Bi ₂ Ir	1.7–2.3		CHf _{0.3} Mo _{0.7}	5.5	B1
Bi ₂ Ir (quenched)	3.0–3.96		CHf _{0.25} Mo _{0.75}	6.6	B1
BiK	3.6		CHf _{0.7} Nb _{0.3}	6.1	B1
Bi ₂ K	3.58	C15	CHf _{0.6} Nb _{0.4}	4.5	B1
BiLi	2.47	L1 _o , α -phase	CHf _{0.5} Nb _{0.5}	4.8	B1
Bi _{4–9} Mg	0.7–~1.0		CHf _{0.4} Nb _{0.6}	5.6	B1
Bi ₃ Mo	3–3.7		CHf _{0.25} Nb _{0.75}	7.0	B1
BiNa	2.25	L1 _o	CHf _{0.2} Nb _{0.8}	7.8	B1
BiNb ₃	4.5	A15-cP8 (Cr ₃ Si)	CHf _{0.9–0.1} Ta _{0.1–0.9}	5.0–9.0	B1
BiNb ₃ (high pressure and temperature)	3.05	A15	CK (excess K)	0.55	Hexagonal
BiNi	4.25	B8 ₁	C ₈ K	0.39	Hexagonal
Bi ₃ Ni	4.06	Orthorhombic	C ₂ La	1.66	tl6 (CaC ₂)
BiNi _{0.5} Rh _{0.5}	3.0	B8 ₁ -hP4 (AsNi)	C ₂ Lu	3.33	Same
Bi _{0.5} NiSb _{0.5}	2.0	Same	C _{0.40–0.44} Mo _{0.60–0.56}	9–13	
Bi _{1–0} Pb _{0–1}	7.26–9.14		C ₃ MoRe	3.8	B1-cF8
Bi _{1–0} Pb _{0–1} (film)	7.25–8.67		C _{0.6} Mo _{4.8} Si ₃	7.6	D8 ₈
Bi _{1–0} Pb _{0.95–0.60}	7.35–8.4	H.C.P. to ϵ -phase	CMo _{0.2} Ta _{0.8}	7.5	B1
Bi ₂ Pb	4.25	t**	CMo _{0.3} Ta _{0.5}	7.7	B1
BiPbSb	8.9		CMo _{0.75} Ta _{0.25}	8.5	B1
Bi _{0.5} Pb _{0.31} Sn _{0.19} (weight fractions)	8.5		CMo _{0.8} Ta _{0.2}	8.7	B1
Bi _{0.5} Pb _{0.25} Sn _{0.25}	8.5		CMo _{0.85} Ta _{0.15}	8.9	B1
BiPd ₂	4.0		CMo _x V _{1-x}	2.9–9.3	B1
Bi _{0.4} Pd _{0.6}	3.7–4	Hexagonal, ordered	CMo _x Zr _{1-x}	9.8	B1
BiPd	3.7	Orthorhombic	C _{0.984} Nb	9.8	B1
			CNb ₂	9.1	
			CNb _x Ti _{1-x}	<4.2–8.8	B1
			CNb _{0.1–0.9} Zr _{0.9–0.1}	4.2–8.4	B1

Substance	T_c , K	Crystal structure type	Substance	T_c , K	Crystal structure type
CRb _x (Au)	0.023–0.151	Hexagonal	Co ₃ Sc ₅ Si ₁₀	5.0	tP38 (Co ₃ Sc ₅ Si ₁₀)
CRe _{0.06} W	5.0		CoSi ₂	1.40; 1.22	C1
CRu	2.00	hP2 (CW)	Co _x Sn _y Yb	2.5	cP40
C _{0.98} Ta	9.7		Co ₃ Th ₇	1.83	D10 ₂
C _{0.848–0.987}	2.04–9.7		Co _x Ti _{1-x}	2.8 (max.)	Co in α -Ti
CTa (film)	5.09	B1	Co _x Ti _{1-x}	3.8 (max.)	Co in β -Ti
CTa ₂	3.26	L' ₃	CoTi ₂	3.44	E9 ₃
CTa _{0.4} Ti _{0.6}	4.8	B1	CoTi	0.71	A2
Cta _{1-0.4} W _{0-0.6}	8.5–10.5	B1	CoU	1.7	B2, distorted
CTa _{0.2-0.9} Zr _{0.8-0.1}	4.6–8.3	B1	CoU ₆	2.29	D2 _c
CTc (excess C)	3.85	Cubic	Co _{0.28} Y _{0.72}	0.34	
CTi _{0.5-0.7} W _{0.5-0.3}	6.7–2.1	B1	CoY ₃	<0.34	
CW	1.0		CoZr ₂	6.3	C16
CW ₂	2.74	L' ₃	Co _{0.1} Zr _{0.9}	3.9	A3
CW ₂	5.2	F.C.C.	Cr _{0.6} Ir _{0.4}	0.4	H.C.P.
C ₂ Y	3.88	tl6 (CaC ₂)	Cr _{0.65} Ir _{0.35}	0.59	H.C.P.
Ca ₃ Co ₄ Sn ₁₃	5.9	cP40 (Pr ₃ Rh ₂ Sn ₁₃)	Cr _{0.7} Ir _{0.3}	0.76	H.C.P.
Ca ₃ Ge ₁₃ Rh ₄	2.1	Same	Cr _{0.72} Ir _{0.28}	0.83	
CaHg	1.6	B2-cP2 (CsCl)	Cr ₃ Ir	0.45	A15
CaHg ₃	1.6	hP8 (Ni ₃ Sn)	Cr _{0-0.1} Nb _{1-0.9}	4.6–9.2	A2
CaIr ₂	6.15	C15	Cr _{0.80} Os _{0.20}	2.5	Cubic
Ca ₃ Ir ₄ Sn ₁₃	7.1	cP40	Cr ₃ Os	4.68	A15-cP8 (Cr ₃ Si)
Ca _x O ₃ Sr _{1-x} Ti (n = 3.7–11 × 10 ¹⁹)	<0.1–0.55		Cr _x Re _{1-x}	1.2–5.2	
Ca _{0.1} O ₃ W	1.4–3.4	Hexagonal	Cr _{0.4} Re _{0.6}	2.15	D8 _b
CaPb	7.0		Cr _{0.8-0.6} Rh _{0.2-0.4}	0.5–1.10	A3
CaRh ₂	6.40	C15	Cr ₃ Rh	0.3	A15-cP8
CaRh _{1.2} Sn _{4.5}	8.7	cP40	Cr ₃ Ru (annealed)	3.3	A15
CaTl ₃	2.0	B2-cP2	Cr ₂ Ru	2.02	D8 _b
Cd _{0.3-0.5} Hg _{0.7-0.5}	1.70–1.92		Cr ₃ Ru ₂	2.10	D8 _b -tP30 (CrFe)
CdHg	1.77; 2.15	Tetragonal	Cr _{0.1-0.3} Ru _{0.9-0.5}	0.34–1.65	A3
Cd _{0.0075-0.05} In _{0.9925-0.95}	3.24–3.36	Tetragonal	Cr _x Ti _{1-x}	3.6 (max.)	Cr in α -Ti
Cd _{0.97} Pb _{0.03}	4.2		Cr _x Ti _{1-x}	4.2 (max.)	Cr in β -Ti
CdSn	3.65		Cr _{0.1} Ti _{0.3} V _{0.6}	5.6	
Cd _{0.17} Tl _{0.83}	2.3		Cr _{0.0175} U _{0.9825}	0.75	β -phase
Cd _{0.18} Tl _{0.82}	2.54		Cs _{0.32} O ₃ W	1.12	Hexagonal
CeCo ₂	0.84	C15	Cu _{0.15} In _{0.85} (film)	3.75	
CeCo _{1.67} Ni _{0.33}	0.46	C15	Cu _{0.04-0.08} In _{0.94-0.92}	4.4	
CeCo _{1.67} Rh _{0.33}	0.47	C15	CuLa	5.85	
Ce _x Gd _{1-x} Ru ₂	3.2–5.2	C15	Cu ₂ Mo ₆ O ₂ S ₆	9	hR15 (Mo ₆ PbS ₈)
CeIr ₃	3.34		Cu ₂ Mo ₆ Se ₈	5.9	Same
CeIr ₅	1.82		Cu _x Pb _{1-x}	5.7–7.7	
Ce _{0.005} La _{0.995}	4.6		CuS	1.62	B18
Ce _x La _{1-x}	1.3–6.3		CuS ₂	1.48–1.53	C18
Ce _x Pr _{1-x} Ru ₂	1.4–5.3	C15	CuSSe	1.5–2.0	C18
Ce _x Pt _{1-x}	0.7–1.55		CuSe ₂	2.3–2.43	C18
CeRu ₂	6.0	C15	CuSeTe	1.6–2.0	C18
Ce ₃ Mo ₆ Se ₅	5.7	hR15 (Mo ₆ PbS ₈)	Cu _x Sn _{1-x}	3.2–3.7	
Ce ₂ Mo ₆ Te ₆	1.7	Same	Cu _x Sn _{1-x} (film, made at 10K)	3.6–7	
Co _x Fe _{1-x} Si ₂	1.4 (max.)	C1	Cu _x Sn _{1-x} (film, made at 300K)	2.8–3.7	
CoHf ₂	0.56	E9 ₃	CuTe ₂	<1.25–1.3	C18
CoLa ₃	4.28		CuTh ₂	3.49	C16
Co ₄ La ₃ Sn ₁₃	2.8	cP40	Cu _{0-0.027} V	3.9–5.3	A2
CoLu ₃	~0.35		CuY	0.33	B2-cP2 (CsCl)
Co _x LuSn _y	1.5	cP40	Cu _x Zn _{1-x}	0.5–0.845	
Co _{0-0.01} Mo _{0.8} Re _{0.2}	2–10		DyMo ₆ S ₈	2.1	hR15
Co _{0.02-0.10} Nb ₃ Rh _{0.98-0.90}	2.28–1.90	A15	Er _x La _{1-x}	1.4–6.3	
Co _x Ni _{1-x} Si ₂	1.4 (max.)	C1	ErMo ₆ S ₈	2.2	hR15
Co _{0.5} Rh _{0.5} Si ₂	2.5		ErMo ₆ Se ₈	6.2	hR15
Co _x Rh _{1-x} Si ₂	3.65 (max.)		Fe ₃ Lu ₂ Si ₅	6.1	tP40 (Fe ₃ Sc ₂ Si ₅)
Co _{-0.3} So _{-0.7}	~0.35		Fe _{0-0.04} Mo _{0.8} Re _{0.2}	1–10	
			Fe _{0.05} Ni _{0.05} Zr _{0.90}	~3.9	

Substance	T_c , K	Crystal structure type	Substance	T_c , K	Crystal structure type
Fe_3Re_2	6.55	$\text{D}8_b$ -tP30 (FeCr)	GeV_3	6.01	A15
$\text{Fe}_3\text{Sc}_2\text{Si}_5$	4.52	tP40	Ge_3Y	3.80	C_c
$\text{Fe}_3\text{Si}_5\text{Tm}$	1.3	Same	$\text{Ge}_{1.62}\text{Y}$	2.4	
$\text{Fe}_3\text{Si}_5\text{Y}_2$	2.4	Same	Ge_2Zr	0.30	$\text{oC}12$ (ZrSi_2)
Fe_3Th_7	1.86	D10	GeZr_3	0.4	$\text{L}1_2$ -tP32 (Ti_3P)
$\text{Fe}_x\text{Ti}_{1-x}$	3.2 (max.)	Fe in α -Ti	$\text{H}_{0.33}\text{Nb}_{0.67}$	7.28	B.C.C.
$\text{Fe}_x\text{Ti}_{1-x}$	3.7 (max.)	Fe in β -Ti	$\text{H}_{0.1}\text{Nb}_{0.9}$	7.38	Same
$\text{Fe}_x\text{Ti}_{0.6}\text{V}_{1-x}$	6.8 (max.)		$\text{H}_{0.05}\text{Nb}_{0.95}$	7.83	Same
FeU_6	3.86	D2 _c	$\text{H}_{0.12}\text{Ta}_{0.88}$	2.81	B.C.C.
$\text{Fe}_{0.1}\text{Zr}_{0.9}$	1.0	A3	$\text{H}_{0.08}\text{Ta}_{0.92}$	3.26	Same
$\text{Ga}_{0.5}\text{Ge}_{0.5}\text{Nb}_3$	7.3	A15	$\text{H}_{0.04}\text{Ta}_{0.96}$	3.62	Same
$\text{Ga}_2\text{Ge}_2\text{U}$	0.87	B2-cP2	HfIrSi	3.50	C37-cP12 (Co_2Si)
GaHf_2	0.21	C16-tI12 (Al_2Cu)	HfMo ₂	0.05	hP24 (Ni_2Mn)
GaLa_3	5.84		HfN _{0.989}	6.6	B1
Ga_3Lu	2.3	B2-cP2	$\text{Hf}_{0-0.5}\text{Nb}_{1-0.5}$	8.3–9.5	A2
Ga_3Mo	9.5		$\text{Hf}_{0.75}\text{Nb}_{0.25}$	> 4.2	
GaMo_3	0.76	A15	HfOs ₂	2.69	C14
GaN (black)	5.85	B4	HfOsP	6.1	C22-hP9 (Fe_2P)
$\text{Ga}_{0.7}\text{Pt}_{0.3}$	2.9	C1	HfPRu	9.9	Same
GapT	1.74	B20	HfRe ₂	4.80	C14
GaSb (120kbar, 77K, annealed)	4.24	A5	$\text{Hf}_{0.14}\text{Re}_{0.86}$	5.86	A12
GaSb (unannealed)	~5.9		$\text{Hf}_{0.99-0.96}\text{Rh}_{0.01-0.04}$	0.85–1.51	
$\text{Ga}_{0-1}\text{Sn}_{1-0}$ (quenched)	3.47–4.18		$\text{Hf}_{0-0.55}\text{Ta}_{1-0.45}$	4.4–6.5	A2
$\text{Ga}_{0-1}\text{Sn}_{1-0}$ (annealed)	2.6–3.85		HfV ₂	8.9–9.6	C15
GaTe	0.17	mC24 (GaTe)	HgIn_{x-1-x}	3.14–4.55	
Ga_5V_2	3.55	Tetragonal (Mn_2Hg_5)	HgIn	3.81	
$\text{GaV}_{4.5}$	9.15		Hg ₂ K	1.20	Orthorhombic
Ga_3Zr	1.38		Hg ₃ K	3.18	
Ga_3Zr_5	3.8	D8 _b -hP16 (Mn_5Si_3)	Hg ₄ K	3.27	
$\text{Gd}_{x}\text{La}_{1-x}$	< 1.0–5.5		Hg ₈ K	3.42	
GdMo_6S_8	3.5	hR15	Hg ₃ Li	1.7	Hexagonal
GdMo_6Se_8	5.6	hR15	HgMg ₃	0.17	hP8 (Na_3As)
$\text{Gd}_{x}\text{Os}_2\text{Y}_{1-x}$	1.4–4.7		Hg ₂ Mg	4.0	tI6 (MoSi_2)
$\text{Gd}_{x}\text{Ru}_2\text{Th}_{1-x}$	3.6 (max.)	C15	Hg_3Mg_5	0.48	D8 _b -hP16 (Mn_5Si_3)
$\text{Ge}_{10}\text{As}_4\text{Y}_5$	9.06	tP38 ($\text{C}0_4\text{Sc}_5\text{Si}_{10}$)	Hg ₃ Na	1.62	Hexagonal
GeIr	4.7	B31	Hg ₆ Na	3.05	
GeIrLa	1.64	tI12 (LaPtSi)	Hg _x Pb _{1-x}	4.14–7.26	
$\text{Ge}_{10}\text{Ir}_5\text{Lu}_5$	2.60	tP38	HgSn	4.2	
$\text{Ge}_{10}\text{Ir}_4\text{Y}_5$	2.62	tP38	Hg _x Tl _{1-x}	2.30–4.19	
Ge ₂ La	1.49; 2.2	Orthorhombic, distorted (Mn_2Hg_5)	Hg ₅ Tl ₂	3.86	
GeLaPt	3.53	tI12	$\text{Ho}_{x}\text{La}_{1-x}$	1.3–6.3	
$\text{Ge}_{13}\text{Lu}_3\text{Os}_4$	3.6	cP40 ($\text{Pr}_3\text{Rh}_2\text{Sn}_{13}$)	$\text{Ho}_{1.2}\text{Mo}_6\text{Se}_8$	6.1	D10 ₂ -hR12 (Be_3Nb)
$\text{Ge}_{10}\text{Lu}_5\text{Rh}_4$	2.79	tP38	$\text{In}_{1-0.86}\text{Mg}_{0-0.14}$	3.395–3.363	
$\text{Ge}_{13}\text{Lu}_3\text{Ru}_4$	2.3	cP40	$\text{In}_2\text{Mo}_6\text{Te}_6$	2.6	hR15 (Mo_6PbS_8)
GeMo ₃	1.43	A15	InNb ₃ (high pressure and temp.)	4–8; 9.2	A15
GeNb ₂	1.9		$\text{In}_{0.5}\text{Nb}_3\text{Zr}_{0.5}$	6.4	
$\text{Ge}_{0.29}\text{Nb}_{0.71}$	6	A15	$\text{In}_{0.11}\text{O}_3\text{W}$	< 1.25–2.8	Hexagonal
GePt	0.40	B31	$\text{In}_{0.95-0.85}\text{Pb}_{0.05-0.15}$	3.6–5.05	
Ge ₃ Rh ₅	2.12	Orthorhombic, related to InNi ₂	$\text{In}_{0.98-0.91}\text{Pb}_{0.02-0.09}$	3.45–4.2	
GeRh	0.96	B31-oP8 (MnP)	InPb	6.65	
$\text{Ge}_{13}\text{Rh}_4\text{Sc}_3$	1.9	c P40	InPd	0.7	B2
$\text{Ge}_{10}\text{Rh}_4\text{Y}_5$	1.35	tP38	InSb (quenched from 170 kbar into liquid N ₂)	4.8	Like A5
$\text{Ge}_{13}\text{Ru}_4\text{Y}_3$	1.7	cP40	InSb	2.1	B4
Ge ₂ So	1.3		(InSb) _{0.95-0.10} Sn _{0.05-0.90} (various heat treatments)	3.8–5.1	
GeTa ₃	8.0	A15-cP8 (Cr_3Si)	(InSb) _{0-0.07} Sn _{1-0.93}	3.67–3.74	
Ge_3Te_4 (n = 1.06×10^{22})	1.55–1.80	Rhombohedral	In ₃ Sn	~5.5	
$\text{Ge}_x\text{Te}_{1-x}$ (n = $8.5-64 \times 10^{20}$)	0.07–0.41	R1	In _x Sn _{1-x}	3.4–7.3	

Substance	T_c , K	Crystal structure type	Substance	T_c , K	Crystal structure type
In _{0.82-1} Te (n = 0.83–1.71 × 10 ²²)	1.02–3.45	B1	Ir ₂ Y ₃	1.61	
In _{1.000} Te _{1.002}	3.5–3.7	B1	Ir ₃ Y	3.50	D10 ₂ -hR13 (Be ₃ Nb)
In ₃ Te ₄ (n = 4.7 × 10 ²¹)	1.15–1.25	Rhombohedral	Ir _x Y _{1-x}	0.3–3.7	
In _x Tl _{1-x}	2.7–3.374		Ir ₂ Zr	4.10	C15
In _{0.8} Tl _{0.2}	3.223		Ir _{0.1} Zr _{0.9}	5.5	A3
In _{0.62} Tl _{0.38}	2.760		K ₂ Mo ₁₅ S ₁₉	3.32	hR15
In _{0.78-0.69} Tl _{0.22-0.31}	3.18–3.32	Tetragonal	K _{0.27-0.31} O ₃ W	0.50	Hexagonal
In _{0.69-0.62} Tl _{0.31-0.38}	2.98–3.3	F.C.C.	K _{0.40-0.57} O ₃ W	1.5	Tetragonal
Ir ₂ La	0.48	C15	La _{0.55} Lu _{0.45}	2.2	Hexagonal, La type
Ir ₃ La	2.32	D10 ₂	La _{0.8} Lu _{0.2}	3.4	Same
Ir ₃ La ₇	2.24	D10 ₂	LaMg ₂	1.05	C15
Ir ₅ La	2.13		LaMo ₆ S ₈	7.1	hR15
IrLaSi ₂	2.03	oC16 (CeNiSi ₂)	LaN	1.35	
IrLaSi ₃	2.7	tl10 (BaNiSn ₃)	LaOs ₂	6.5	C15
Ir ₂ Lu	2.47	C15	LaPt ₂	0.46	C15
Ir ₃ Lu	2.89	C15	La _{0.28} Pt _{0.72}	0.54	C15
Ir ₄ Lu ₅ Si ₁₀	3.9	tP38 (Co ₄ Sc ₅ Si ₁₀)	LaPtSi	3.48	tl12
IrMo	< 1.0	A3	LaRh ₃	2.60	
IrMo ₃	9.6	A15	LaRh ₅	1.62	
IrMo ₃	6.8	D8 _b	La ₂ Rh ₃	2.58	D10 ₂
IrNb ₃	1.9	A15	LaRhSi ₂	3.42	oC16 (CeNiSi ₂)
Ir _{0.4} Nb _{0.6}	9.8	D8 _b	La ₂ Rh ₃ Si ₅	4.45	oI40 (Co ₃ Si ₅ U ₂)
Ir _{0.37} Nb _{0.63}	2.32	D8 _b	LaRhSi ₃	2.7	tl10 (BaNiSn ₃)
IrNb	7.9	D8 _b	LaRh ₂ Si ₂	3.90	tl10 (Al ₄ Ba)
Ir _{1.15} Nb _{0.85}	4.6	oP12 (IrTa)	LaRu ₂	1.63	C15
Ir _{0.02} Nb ₃ Rh _{0.98}	2.43	A15	La ₃ S ₄	6.5	D7 ₃
Ir _{0.05} Nb ₃ Rh _{0.95}	2.38	A15	La ₃ Se ₄	8.6	D7 ₃
Ir _{0.287} O _{0.14} Ti _{0.573}	5.5	E9 ₃	LaSi ₂	2.3	C _c
Ir _{0.265} O _{0.035} Ti _{0.65}	2.30	E9 ₃	La _x Y _{1-x}	1.7–5.4	
Ir _x Os _{1-x}	0.3–0.98		LaZn	1.04	B2
Ir _{1.5} Os _{0.5}	2.4	C14	Li ₂ Mo ₆ S ₈	4.2	hR15
IrOsY	2.6	C15	LiPb	7.2	
IrSiY	2.70	C37-oP12 (Co ₂ Si)	LuOs ₂	3.49	C14
IrSiZr	2.04	Same	Lu _{0.275} Rh _{0.725}	1.27	C15
Ir ₂ Sc	2.07	C15	LuRh ₅	0.49	
Ir _{2.5} Sc	2.46	C15	Lu ₅ Rh ₄ Si ₁₀	3.95	tP38 (Co ₄ So ₅ Si ₁₀)
Ir ₄ Sc ₅ Si ₁₀	8.46	tP38	LuRu ₂	0.86	C14
Ir ₂ Si ₂ Th	2.14	tl10	Mg _{1.14} Mo _{6.6} S ₈	3.5	hR15
IrSi ₃ Th	1.75	tl10	Mg ₂ Nb	5.6	
IrSiTh	6.50	tl12 (LaPtSi)	Mg _{0.47} Tl _{~0.53}	2.75	B2
Ir ₂ Si ₂ Y	2.60	tl10 (Al4Ba)	MgZn	0.9	A3-oP4 (AuCd)
Ir ₄ Si ₁₀ Y ₅	3.10	tP38	Mn _x Ti _{1-x}	2.3 (max.)	Mn in -Ti
Ir ₃ Si ₅ Y ₂	2.83	oI40	Mn _x Ti _{1-x}	1.1–3.0	Mn in -Ti
IrSn ₂	0.65–0.78	C1	MnU ₆	2.32	D2 _c
Ir ₂ Sr	5.70	C15	Mo ₂ N	5.0	F.C.C.
Ir ₇ Ta ₁₃	1.2	D8 _b -tP30 (FeCr)	Mo ₆ Na ₂ S ₈	8.6	hR15
Ir _{0.5} Te _{0.5}	~3		Mo _x Nb _{1-x}	0.016–9.2	
IrTe ₃	1.18	C2	Mo _{5.25} Nb _{0.75} Se ₈	6.2	hR15
IrTh	< 0.37	B ₁	Mo ₆ NdS ₈	8.2	
Ir ₂ Th	6.50	C15	Mo ₃ Os	7.2	A15
Ir ₃ Th	4.71		Mo _{0.62} Cs _{0.38}	5.65	D8 _b
Ir ₃ Th ₇	1.52	D10 ₂	Mo ₃ P	5.31	DO _c
Ir ₅ Th	3.93	D2 _d	Mo ₆ Pb _{1.2} Se ₈	6.75	hR15
IrTi ₃	5.40	A15	Mo _{0.5} Pd _{0.5}	3.52	A3
IrV ₂	1.39	A15	Mo ₆ PrSe ₈	9.2	hR15
IrW ₃	3.82		MoRe	7.8	D8 _b -tP30
Ir _{0.28} W _{0.72}	4.49		MoRe ₃	9.25; 9.89	A12
Ir ₂ Y	2.18; 1.38	C15	Mo _x Re _{1-x}	1.2–12.2	
Ir _{0.69} Y _{0.31}	1.98; 1.44	C15	Mo _{0.42} Re _{0.58}	6.35	D8 _b
Ir _{0.70} Y _{0.30}	2.16	C15	MoRh	1.97	A3
			Mo _x Rh _{1-x}	1.5–8.2	B.C.C.

Substance	T_c , K	Crystal structure type	Substance	T_c , K	Crystal structure type
MoRu	9.5–10.5	A3	Nb ₃ Rh	2.64	A15
Mo _{0.61} Ru _{0.39}	7.18	D8 _b	Nb _{0.6} Rh _{0.40}	4.21	D8 _b plus other
Mo _{0.2} Ru _{0.8}	1.66	A3	Nb _{0.9} Rh _{1.1}	3.07	A3-oP4 (AuCd)
Mo ₅ Ru ₂	7.0	D8 _b -tP30	Nb _x Rh _{0.98–0.90} Ru _{0.02–0.10}	2.42–2.44	A15
Mo ₄ Ru ₂ Te ₈	1.7	hR15	Nb _x Ru _{1-x}	1.2–4.8	
Mo ₆ S ₈	1.85	hR15	NbRuSi	2.65	oI36
Mo ₆ S ₈ Sc	3.6	hR15	NbS ₂	6.1–6.3	Hexagonal, NbSe ₂ type
Mo ₆ S ₈ Sm _{1.2}	2.9	hR15	NbS ₂	5.0–5.5	Hexagonal, three-layer type
Mo ₆ S ₈ Tb	2.0	hR15	Nb ₃ Sb	0.2	L1 ₂ -tP32 (Ti ₃ P)
Mo ₆ S ₈ Tl	8.7	hR15	Nb ₃ Sb _{0–0.7} Sn _{1–0.3}	6.8–18	A15
Mo ₆ S ₈ Tm _{1.2}	2.1	hR15	NbSe ₂	5.15–5.62	Hexagonal
Mo ₆ S ₈ Y _{1.2}	3.0	hR15	Nb _{1–1.05} Se ₂	2.2–7.0	Same
Mo ₆ S ₈ Yb	9.2	hR15	Nb ₃ Se ₄	2.0	hP14
Mo _{6,6} S ₈ Zn ₁₁	3.6	hR15	Nb ₃ Si	1.5	L1 ₂
Mo ₃ Sb ₄	2.1		Nb ₃ SiSnV ₃	4.0	
Mo ₆ Se ₈	6.3	hR15	NbSn ₂	2.60	Orthorhombic
Mo ₆ Se ₈ Sm _{1.2}	6.8	hR15	Nb ₆ Sn ₅	2.8	oI44 (Sn ₅ Ti ₆)
Mo ₆ Se ₈ Tn _{1.2}	6.8	hR15	NbSnTaV	6.2	A15
Mo ₆ Se ₈ Tb	5.7	hR15	NbSnV ₂	5.5	A15
Mo ₃ Se ₃ Tl	4.0	hP14	Nb ₃ SnV	9.8	A15
Mo ₆ Se ₈ Tm _{1.2}	6.3	hR15	Nb _x Ta _{1-x}	4.4–9.2	A2
Mo ₆ Se ₈ Yb	6.2	hR15	Nb ₃ Te ₄	1.8	hP14
Mo ₃ Si	1.30	A15	Nb _x Ti _{1-x}	0.6–9.8	
MoSi _{0.7}	1.34		Nb _{0.6} Ti _{0.4}	9.8	
Mo _x SiV _{3-x}	4.54–16.0	A15	Nb _x U _{1-x}	1.95 (max.)	
Mo _{5.25} Ta _{0.75} Te ₈	1.7	hR15	Nb _{0.88} V _{0.12}	5.7	A2
Mo ₆ Te ₈	1.7	hR15	Nb _{0.5} V _{1.5} Zr	4.3	C15-hP12 (MgZn ₂)
Mo _{0.16} Ti _{0.84}	4.18; 4.25		Ni _{0.3} Th _{0.7}	1.98	D10 ₂
Mo _{0.913} Ti _{0.087}	2.95		NiZr ₂	1.52	
Mo _{0.04} Ti _{0.96}	2.0	Cubic	Ni _{0.1} Zr _{0.9}	1.5	A3
Mo _{0.025} Ti _{0.975}	1.8		O ₃ Rb _{0.27–0.29} W	1.98	Hexagonal
Mo _x U _{1-x}	0.7–2.1		OSn _x	3.81	tP4 (PbO)
Mo _x V _{1-x}	0–5.3		O ₃ SrTi (n = 1.7–12.0 × 10 ¹⁹)	0.12–0.37	
Mo ₂ Zr	4.25–4.75	C15	O ₃ SrTi (n = 10 ¹⁸ –10 ²¹)	0.05–0.47	
NNb (film)	6–9	B1	O ₃ SrTi (n = 10 ²⁰)	0.47	
N _x O _y Ti _z	2.9–5.6	Cubic	O ₃ Sr _{0.08} W	2–4	Hexagonal
N _x O _y V _z	5.8–8.2	Cubic	OTi	0.58	
N _{0.34} Re	4–5	F.C.C.	O ₃ Tl _{0.30} W	2.0–2.14	Hexagonal
NTa (film)	4.84	B1	OV ₃ Zr ₃	7.5	E9 ₃
N _{0.6–0.987} Ti	< 1.17–5.8	B1	OW ₃ (film)	3.35; 1.1	A15
N _{0.82–0.99} V	2.9–7.9	B1	OsPti	1.2	C22-hP9 (Fe ₂ P)
NZr	9.8	B1	OsPZr	7.4	Same
N _{0.906–0.984} Zr	3.0–9.5	B1	OsReY	2.0	C14
Na _{0.28–0.35} O ₃ W	0.56	Tetragonal	Os ₃ Sc	4.6	C14
Na _{0.28} Pb _{0.72}	7.2		OsTa	1.95	A12
NbO	1.25		Os ₃ Th ₇	1.51	D10 ₂
NbOs ₂	2.52	A12	Os _x W _{1-x}	0.9–4.1	
Nb ₃ Os	1.05	A15	OsW ₃	~3	
Nb _{0.6} Os _{0.4}	1.89; 1.78	D8 _b	Os ₂ Y	4.7	C14
Nb ₃ Os _{0.02–0.10} Rh _{0.98–0.90}	2.42–2.30	A15	Os ₂ Zr	3.0	C14
Nb ₃ P	1.8	L1 ₂ -tP32 (Ti ₃ P)	Os _x Zr _{1-x}	1.5–5.6	
NbPRh	4.08	C37-oP12 (Co ₂ Si)	PPb	7.8	
Nb _{0.6} Pd _{0.4}	1.60	D8 _f plus cubic	OsW ₂	3.81	D8 _b -tP30 (FeCr)
Nb ₃ Pd _{0.02–0.10} Rh _{0.92–0.90}	2.49–2.55	A15	PPd _{3.0–3.2}	<0.35–0.7	DO ₁₁
Nb _{0.62} Pt _{0.38}	4.21	D8 _b	P ₃ Pd ₇ (high temperature)	1.0	Rhombohedral
Nb ₅ Pt ₃	3.73	D8 _b	P ₃ Pd ₇ (low temperature)	0.70	Complex
Nb ₃ Pt _{0.02–0.98} Rh _{0.98–0.02}	2.52–9.6	A15	PRh	1.22	
NbRe ₃	5.27	D8 _b -tP30 (FeCr)	PRh ₂	1.3	C1
Nb _{0.38–0.18} Re _{0.62–0.82}	2.43–9.70	A15	P ₄ Rh ₅	1.22	oP28 (CaFe ₂ O ₄)
NbRe	3.8	D8 _b -tP30	PRhTa	4.41	C37-oP12 (Co ₂ Si)
NbReSi	5.1	oI36 (FeTiSi)			

Substance	T_c , K	Crystal structure type	Substance	T_c , K	Crystal structure type
PRhZr	1.55	Same	PtV _{3.5}	1.26	A15
PRuTi	1.3	C22-hP9 (Fe ₂ P)	Pt _{0.5} W _{0.5}	1.45	A1
PRuZr	3.46	C37-oP12	Pt _x W _{1-x}	0.4–2.7	
PW ₃	2.26	DO _e	Pt ₂ Y ₃	0.90	
Pb ₂ Pd	2.95	C16	Pt ₂ Y	1.57; 1.70	C15
Pb ₄ Pt	2.80	Related to C16	Pt ₃ Y ₇	0.82	D10 ₂
Pb ₂ Rh	2.66	C16	PtZr	3.0	A3
PbSb	6.6		Re ₂ Sc	4.2	C15-hP12 (MgZn ₂)
PbTe (plus 0.1 w/o Pb)	5.19		Re ₂₄ Sc ₅	2.2	A12-cl58 (Mg)
PbTe (plus 0.1 w/o Te)	5.24–5.27		ReSiTa	4.4	oI36 (FeTiSi)
PbTl _{0.27}	6.43		Re ₃ Si ₅ Y ₂	1.76	tP40 (Fe ₃ Sc ₂ Si ₃)
PbTl _{0.17}	6.73		Re ₃ Ta ₂	1.4	D8 _b -tP30 (FeCr)
PbTl _{0.12}	6.88		Re _{0.64} Ta _{0.36}	1.46	A12
PbTl _{0.075}	6.98		Re ₃ Ta	6.78	A12-cl58 (Mn)
PbTl _{0.04}	7.06		Re ₂₄ Ti ₅	6.60	A12
Pb _{1-0.26} Tl _{0-0.74}	7.20–3.68		Re _x Ti _{1-x}	6.6 (max.)	
PbTl ₂	3.75–4.1		Re _{0.76} V _{0.24}	4.52	D8 _b
Pb ₃ Zr ₅	4.60	D8 _s	Re ₃ V	6.26	D8 _b -tP30
PbZr ₃	0.76	A15	Re _{0.92} V _{0.08}	6.8	A3
Pd _{0.9} Pt _{0.1} Te ₂	1.65	C6	Re _{0.6} W _{0.4}	6.0	
Pd _{0.05} Ru _{0.05} Zr _{0.9}	~9		Re _{0.5} W _{0.5}	5.12	D8 _b
Pd _{2.2} S (quenched)	1.63	Cubic	Re ₁₃ W ₁₂	5.2	D8 _b -tP30
PdSb ₂	1.25	C2	Re ₃ W	9.0	A12-cl58
PdSb	1.5	B8 ₁	Re ₂ Y	1.83	C14
PdSbSe	1.0	C2	Re ₂ Zr	5.9	C14
PdSbTe	1.2	C2	Re ₃ Zr	7.40	A12-cl58
Pd ₄ Se	0.42	Tetragonal	Re ₆ Zr	7.40	Same
Pd ₆₋₇ Se	0.66	Like Pd ₄ Te	Rh ₁₇ S ₁₅	5.8	Cubic
Pd _{2.8} Se	2.3		Rh _{~0.24} Sc _{~0.76}	0.88; 0.92	
Pd _x Se _{1-x}	2.5 (max.)		Rh ₄ Sc ₅ Si ₁₀	8.54	tP38
PdSi	0.93	B31	Rh ₄ Sc ₃ Sn ₁₃	4.5	cP40
PdSn	0.41	B31	Rh _x Se _{1-x}	6.0 (max.)	
PdSn ₂	3.34		RhSi ₃ Th	1.76	tI10
Pd ₂ Sn	0.41	C37	Rh _{0.86} Sc _{1.04} Th	6.45	tI12
Pd ₃ Sn	0.47–0.64	B8 ₂	Rh ₂ Si ₂ Y	3.11	tI10
Pd ₃ SnTm	1.77	DO ₃ -cF16 (BiF ₃)	Rh ₃ Si ₅ Y ₂	2.70	oI40
Pd ₂ SnY	4.92	Same	Rh ₄ Sn ₁₃ Sr ₃	4.3	cP40
Pd ₂ SnYb	1.79	Same	Rh _x Sn _y Th	1.9	cI2 (W)
PdTe	2.3; 3.85	B8 ₁	Rh ₃ Sn ₁₃ Y ₃	2.3	cP40
PdTe _{1.02-1.08}	2.56–1.88	B8 ₁	Rh ₅ Sn ₇	3.2	cP40
PdTe ₂	1.69	C6	Rh ₆ Sn ₇	6.2	C15
PdTe _{2.1}	1.89	C6	Rh _{0.4} Ta _{0.6}	2.35	D8 _b
PdTe _{2.3}	1.85	C6	RhTe ₂	1.51	C2
Pd _{1.1} Te	4.07	B8 ₁	Rh _{0.67} Te _{0.33}	0.49	
Pd ₃ Te	0.76	cI2 (W)	Rh _x Te _{1-x}	1.51 (max.)	
PdTh ₂	0.85	C16	RhTh	0.36	B _f
Pd _{0.01} Zr _{0.9}	7.5	A3	Rh ₃ Th ₇	2.15	D10 ₂
PtSb	2.1	B8 ₁	Rh ₅ Th	1.07	
PtSi	0.88	B31	Rh _x Ti _{1-x}	2.25–3.95	
PtSn	0.37	B8 ₁	Rh _{0.02} U _{0.98}	0.96	
PtSn ₄	2.38	C16-oC20 (PdSn ₄)	RhV ₃	0.38	A15
Pt ₃ Ta ₇	1.5	D8 _b -tP30	RhW	~3.4	A3
PtTa ₃	0.4	A15-cP8 (Cr ₃ Si)	Rh ₃ Y ₃	0.65	
PtTe	0.59	Orthorhombic	Rh ₂ Y ₃	1.48	
PtTh	0.44	B _f	Rh ₃ Y	1.07	C15
Pt ₃ Th ₇	0.98	D10 ₂	Rh ₅ Y	0.56	
Pt ₅ Th	3.13		Rh ₃ Y ₇	0.32	hP20 (Fe ₃ Th ₇)
PtTi ₃	0.58	A15	Rh _{0.005} Zr (annealed)	5.8	
Pt _{0.02} U _{0.98}	0.87	β -phase	Rh _{0-0.45} Zr _{1-0.55}	2.1–10.8	
PtV _{2.5}	1.36	A15	Rh _{0.1} Zr _{0.9}	9.0	H.C.P.
PtV ₃	2.87–3.20	A15	Ru ₂ Sc	1.67	C14
			RuSiTa	3.15	oI36

Substance	T_c , K	Crystal structure type
Ru ₃ Si ₂ Th	3.98	hP12
Ru ₃ Si ₂ Y	3.51	hP12
Ru _{1.1} Sn _{3.1} Y	1.3	cP40
Ru ₂ Th	3.56	C15
RuTi	1.07	B2
Ru _{0.05} Ti _{0.95}	2.5	
Ru _{0.1} Ti _{0.9}	3.5	
Ru _x Ti _{0.6} V _y	6.6 (max.)	L1 ₂ -cP4
Ru ₃ U	0.15	
Ru _{0.45} V _{0.55}	4.0	B2
RuW	7.5	A3
Ru ₂ Y	1.52	C14
Ru ₂ Zr	1.84	C14
Ru _{0.1} Zr _{0.9}	5.7	A3
STh	0.5	B1-cF8 (NaCl)
SbSn	1.30–1.42	B1 or distorted
SbTa ₃	0.72	A15-cP8 (Cr ₃ Si)
SbTi ₃	5.8	Same
Sb ₂ Ti ₇	5.2	
Sb _{0.01–0.03} V _{0.99–0.97}	3.76–2.63	A2
SbV ₃	0.80	A15
SeTh	1.7	B1-cF8
SiMo ₃	1.4	A15-cP8
Si ₂ Th	3.2	C _o , α -phase
Si ₂ Th	2.4	C32, β -phase
SiV _{2.7} Ru _{0.3}	2.9	A15
Si ₂ W ₃	2.8; 2.84	
SiZr ₃	0.5	L1 ₂ -tP32 (Ti ₃ P)
Sn _{0.174–0.104} Ta _{0.826–0.896}	6.5–< 4.2	A15
SnTa ₃	8.35	A15, highly ordered
SnTa ₃	6.2	A15, partially ordered
SnTaV ₂	2.8	A15
SnTa ₂ V	3.7	A15
Sn _x Te _{1-x} (n = 10.5–20 × 10 ²⁰)	0.07–0.22	B1
Sn ₃ Th	3.33	L1 ₂ -cP4
SnTi ₃	5.80	A15-cP8
Sn _x Tl _{1-x}	2.37–5.2	
SnV ₃	3.8	A15
Sn _{0.02–0.057} V _{0.98–0.943}	2.87–~1.6	A2
SnZr ₃	0.92	A15-cP8
Ta _{0.025} Ti _{0.975}	1.3	Hexagonal
Ta _{0.05} Ti _{0.95}	2.9	Hexagonal
Ta _{0.05–0.75} V _{0.95–0.25}	4.30–2.65	A2
Ta _{0.8–1} W _{0.2–0}	1.2–4.4	A2
Tc _{0.1–0.4} W _{0.9–0.6}	1.25–7.18	Cubic
Tc _{0.50} W _{0.50}	7.52	α plus
Tc _{0.60} W _{0.40}	7.88	plus α
Tc ₆ Zr	9.7	A12
TeY	1.02	B1-cF8
ThTl ₃	0.87	L1 ₂ -cP4
Th _{0–0.55} Y _{1–0.45}	1.2–1.8	
Ti _{0.70} V _{0.30}	6.14	Cubic
Ti _x V _{1-x}	0.2–7.5	
Ti _{0.5} Zr _{0.5} (annealed)	1.23	
Ti _{0.5} Zr _{0.5} (quenched)	2.0	
Tl ₃ Y	1.52	L1 ₂ -cP4
V ₂ Zr	8.80	C15
V _{0.26} Zr _{0.74}	5.9	
W ₂ Zr	2.16	C15
YZn	0.33	B2-cP2 (CsCl)

* n denotes current carriers concentration in cm⁻³.

B. Superconductors with $T_c > 10$ K		
Substance	T_c , K	Crystal structure type
Al ₂ CMo ₃	10.0	A13
Al _{0.5} Ge _{0.5} Nb	12.6	A15
Al _{~0.8} Ge _{~0.2} Nb ₃	20.7	A15
AlNb ₃	18.0	A15
AlNb ₃	12.0	(Cr ₃ Si) (FeCr)
A1Nb _{1-x}	<4.2–13.5	D8 _b
A1Nb _{1-x}	12–17.5	A15
A1Nb _{0.73–0.48} V _{0–0.25}	14.5–17.5	A15
A1Nb _x	4.4–13.5	
A1 _{0.1} Si _{0.9} V ₃	14.05	
A1V ₃	11.8	A15
AuNb ₃	11.5	A15
Au _{0–0.3} Nb _{1–0.7}	1.1–11.0	
Au _{0.02–0.98} Nb ₃ Rh _{0.98–0.02}	2.53–10.9	A15
AuNb _{3(1-x)} V _{3x}	1.5–11.0	A15
B _{0.03} C _{0.51} Mo _{0.47}	12.5	
B ₄ LuRh ₄	11.7	(B ₄ CeCo ₄)
B ₂ LuRu	10	
B ₄ Rh ₄ Y	11.3	(B ₄ CeCo ₄)
B _{0.1} Si _{0.9} V ₃	15.8	A15
BaBi _{0.2} O ₃ Pb _{0.8}	13.2	
Ba ₂ CaCu ₂ O ₈ Tl ₂	120	
Ba ₂ Cu ₃ LaO ₆	80	
Ba ₂ Cu ₃ O ₇ TM	101	
Ba ₂ Cu ₃ O ₇ Y	90	
(Ba,La) ₂ CuO ₄	36	A15
Bi ₂ CaCu ₂ O ₈ Sr ₂	110	
Br ₂ Mo ₆ S ₆	13.8	(Mo ₆ PbS ₈)
C ₃ La	11.0	(C ₃ Pu ₂)
CMo	14.3	B1
CMo ₂	12.2	o**
C _{0.5} Mo _x Nb _{1-x}	10.8–12.5	B1
CMo _x Ti _{1-x}	10.2(max)	B1
CMo _{0.83} Ti _{0.17}	10.2	B1
C _{0–0.38} N _{1–0.62} Ta	10.0–11.3	
CNb (whiskers)	7.5–10.5	
CNb	11.5	B1
C _{0.7–1.0} Nb _{0.3–0}	6–11	B1
CNb _x Ta _{1-x}	8.2–13.9	
CNb _{0.6–0.9} W _{0.4–0.1}	12.5–11.6	B1
C _{0.1} Si _{0.9} V ₃	16.4	A15
CTa	10.3	B1
CTa _{1–0.4} W _{0–0.6}	8.5–10.5	B1
C _{0.66} Th _{0.13} Y _{0.21}	17	(C ₃ Pu ₂)
C ₃ Y ₂	11.5	(C ₃ Pu ₂)
CW	10	B1
(Ca,La) ₂ CuO ₄	18	(K ₂ NiF ₄)
Cu(La,Sr) ₂ O ₄	39	
Cu _{1.8} Mo ₆ S ₈	10.8	(Mo ₆ PbS ₈)
Cr _{0.3} SiV _{2.7}	11.3	A15
GaNb ₃	14.5	A15
GaN _x V ₃ Sn _{1-x}	14–18.37	A15
GaV ₃	16.8	A15
GaV _{2.1–3.5}	6.3–14.45	A15
GeNb ₃	23.2	A15
GeNb ₃ (quenched)	6–17	A15
Ge _x Nb ₃ Sn _{1-x}	17.6–18.0	A15
Ge _{0.5} Nb ₃ Sn _{0.5}	11.3	
Ge _{0.1} Si _{0.9} V ₃	14.0	A15
GeV ₃	11	A15
InLa ₃	9.83; 10.4	LI ₂
		(AuCu ₃)

Substance	T_c K	Crystal structure type	Substance	T_c K	Crystal structure type
In _{0-0.3} Nb ₃ Sn _{1-0.7}	18.0–18.19	A15	N _{100-42w/o} Nb _{0-58w/o} Ti	15–16.8	
InV ₃	13.9	A15	N _{100-75w/o} Nb _{0-25w/o} Zr	12.5–16.35	
Ir _{0.4} Nb _{0.6}	10	(FeCr)	NNb _x Zr _{1-x}	9.8–13.8	B1
LaMo ₆ Se ₈	11.4	(Mo ₆ PbS ₈)	N _{0.93} Nb _{0.85} Zr _{0.15}	13.8	B1
LiO ₄ Ti ₂	13.7	(A ₁ ₂ MgO ₄)	NTa	12–14	B1
MgB ₂	39.0±0.5	C32	NZr	10.7	B1
MoN	12; 14.8		Nb ₃ Pt	10.9	A15
Mo ₃ Os	12.7	A15	Nb _{0.18} Re _{0.82}	10	(Mn)
Mo ₆ Pb _{0.9} S _{7.5}	15.2	(Mo ₆ PbS ₈)	Nb ₃ Si	19	A15
Mo ₃ Re	10.0; 15	A15	Nb _{0.3} SiV _{2.7}	12.8	A15
Mo _x Re _{1-x}	1.2–12.2		Nb ₃ Sn	18.05	A15
Mo _{0.52} Re _{0.48}	11.1		Nb _{0.8} Sn _{0.2}	18.18; 18.5	A15
Mo _{0.57} Re _{0.43}	14.0		Nb _x Sn _{1-x} (film)	2.6–18.5	o*
Mo _{~0.60} Re _{0.395}	10.6		Nb ₃ Sn ₂	16.6	t*
MoRu	9.5–10.5	A3	NbSnTa ₂	10.8	A15
Mo ₃ Ru	10.6	A15	Nb ₂ SnTa	16.4	A15
Mo ₆ Se ₈ T1	12.2	(Mo ₆ PbS ₈)	Nb _{2.5} SnTa _{0.5}	17.6	A15
Mo _{0.3} SiV _{2.7}	11.7	A15	Nb _{2.75} SnTa _{0.25}	17.8	A15
Mn ₃ Si	12.5	A15	Nb _{3x} SnTa _{3(1-x)}	6.0–18.0	
Mo ₃ Tc	15	A15	Nb ₂ SnTa _{0.5} V _{0.5}	12.2	A15
Mo _{0.3} Tc _{0.7}	12.0	A15	NbTc ₃	10.5	A12
Mo _x Tc _{1-x}	10.8–15.8		Nb _{0.75} Zr _{0.25}	10.8	
MoTc ₃	15.8		Nb _{0.66} Zr _{0.33}	10.8	
NNb (whiskers)	10–14.5		PbTa ₃	17	A15
NNb (diffusion wires)	16.10		RhTa ₃	10	A15
N _{0.988} Nb	14.9; 17.3	B1	RhZr ₂	10.8; 11.3	C16 (A ₁ ₂ Cu)
N _{0.824-0.988} Nb	14.4–15.3	B1	Rh _{0-0.45} Zr _{1-0.55}	2.1–10.8	
N _{0.7-0.795} Nb	11.3–12.9		SiTi _{0.3} V _{2.7}	10.9	A15
NNb _x O _y	13.5–17.0	B1	SiV ₃	17.1	A15
NNb _x O _y	6.0–11		SiV _{2.7} Zr _{0.3}	13.2	A15

TABLE 5. Critical Field Data

Substance	H_o (oersteds)	Substance	H_o (oersteds)
Ag ₂ F	2.5	InSb	1100
Ag ₃ NO ₁₁	57	In _x Tl _{1-x}	252–284
Al ₂ CMo ₃	1700	In _{0.8} Tl _{0.2}	252
BaBi ₃	740	Mg _{0.47} Tl _{0.53}	220
Bi ₂ Pt	10	Mo _{0.16} Ti _{0.84}	<985
Bi ₃ Sr	530	NbSn ₂	620
Bi ₅ Tl ₃	>400	PbTl _{0.27}	756
CdSn	>266	PbTl _{0.17}	796
CoSi ₂	105	PbTl _{0.12}	849
Cr _{0.1} Ti _{0.3} V _{0.6}	1360	PbTl _{0.075}	880
In _{1-0.86} Mg _{0-0.14}	272.4–259.2	PbTl _{0.04}	864

TABLE 6. High Critical Magnetic-Field Superconductive Compounds and Alloys

Substance	T_c , K	H_{c1} , kOe	H_{c2} , kOe	H_{c3} , kOe	T_{obs} , K ^a
Al_2CMo_3	9.8–10.2	0.091	156		1.2
AlNb_3		0.375			
$\text{Ba}_x\text{O}_3\text{Sr}_{1-x}\text{Ti}$	<0.1–0.55	0.0039 max.			
$\text{Bi}_{0.5}\text{Cd}_{0.1}\text{Pb}_{0.27}\text{Sn}_{0.13}$			>24		3.06
$\text{Bi}_x\text{Pb}_{1-x}$	7.35–8.4	0.122 max.	30 max.		4.2
$\text{Bi}_{0.56}\text{Pb}_{0.44}$	8.8		15		4.2
$\text{Bi}_{7.5w/o}\text{Pb}_{92.5w/o}$			2.32		
$\text{Bi}_{0.099}\text{Pb}_{0.901}$		0.29	2.8		
$\text{Bi}_{0.02}\text{Pb}_{0.98}$		0.46	0.73		
$\text{Bi}_{0.53}\text{Pb}_{0.32}\text{Sn}_{0.16}$			>25		3.06
$\text{Bi}_{1.93}\text{Sn}_{0.07}$			0–0.032		3.7
Bi_xTl_3	6.4		>5.6		3.35
C_8K (excess K)	0.55		0.160 ($\text{H} \perp c$) 0.730 ($\text{H} c$)		0.32
C_8K	0.39		0.025 ($\text{H} \perp c$) 0.250 ($\text{H} c$)		0.32
$\text{C}_{0.44}\text{Mo}_{0.56}$	12.5–13.5	0.087	98.5		1.2
CNb	8–10	0.12	16.9		4.2
$\text{CNb}_{0.4}\text{Ta}_{0.6}$	10–13.6	0.19	14.1		1.2
CTa	9–11.4	0.22	4.6		1.2
$\text{Ca}_x\text{O}_3\text{Sr}_{1-x}\text{Ti}$	<0.1–0.55	0.002–0.004			
$\text{Cd}_{0.1}\text{Hg}_{0.9}$ (by weight)		0.23	0.34		2.04
$\text{Cd}_{0.05}\text{Hg}_{0.95}$		0.28	0.31		2.16
$\text{Cr}_{0.10}\text{Ti}_{0.30}\text{V}_{0.60}$	5.6	0.071	84.4		0
GaN	5.85	0.725			4.2
$\text{Ga}_x\text{Nb}_{1-x}$			>28		4.2
GaSb (annealed)	4.24		2.64		3.5
$\text{GaV}_{1.95}$	5.3		73 ^c		
$\text{GaV}_{2.1-3.5}$	6.3–14.45		230–300 ^d		0
GaV_3		0.4	350 ^e 500 ^d		0
$\text{GaV}_{4.5}$	9.15		121 ^c		0
Hf_xNb_y			>52–>102		1.2
Hf_xTa_y			>28–>86		1.2
$\text{Hg}_{0.05}\text{Pb}_{0.95}$		0.235	2.3		
$\text{Hg}_{0.10}\text{Pb}_{0.899}$		0.23	4.3		4.2
$\text{Hg}_{0.15}\text{Pb}_{0.85}$	6.75		>13		2.93
$\text{In}_{0.98}\text{Pb}_{0.02}$	3.45	0.1		0.12	2.76
$\text{In}_{0.96}\text{Pb}_{0.04}$	3.68	0.1	0.12	0.25	2.94
$\text{In}_{0.94}\text{Pb}_{0.06}$	3.90	0.095	0.18	0.35	3.12
$\text{In}_{0.913}\text{Pb}_{0.087}$	4.2	~10.17	0.55	2.65	
$\text{In}_{0.316}\text{Pb}_{0.684}$		0.155	3.7		4.2
$\text{In}_{0.17}\text{Pb}_{0.83}$			2.8	5.5	4.2
$\text{In}_{1.00}\text{Te}_{1.002}$	3.5–3.7		1.2 ^c		0
$\text{In}_{0.95}\text{Ti}_{0.05}$		0.263	0.263		3.3
$\text{In}_{0.90}\text{Ti}_{0.10}$		0.257	0.257		3.25
$\text{In}_{0.83}\text{Ti}_{0.17}$		0.242	0.39		3.21
$\text{In}_{0.75}\text{Ti}_{0.25}$		0.216	0.50		3.16
LaN	1.35	0.45			0.76
La_3S_4	6.5	≈0.15	>25		1.3
La_3Se_4	8.6	≈0.2	>25		1.25
$\text{Mo}_{0.52}\text{Re}_{0.48}$	11.1		14–21 18–28	22–33 37–43	4.2 1.3
$\text{Mo}_{0.6}\text{Re}_{0.395}$	10.6		14–20 19–26	20–37 26–37	4.2 1.3
$\text{Mo}_{0.5}\text{Ti}_{0.5}$			75 ^c		0
$\text{Mo}_{0.16}\text{Ti}_{0.84}$	4.18	0.028	98.7 ^c 36–38		0 3.0
$\text{Mo}_{0.913}\text{Ti}_{0.087}$	2.95	0.060	15		4.2
$\text{Mo}_{0.1-0.3}\text{U}_{0.9-0.7}$	1.85–2.06		>25		
$\text{Mo}_{0.17}\text{Zr}_{0.83}$			30		

Substance	T_c , K	H_{c1} , kOe	H_{c2} , kOe	H_{c3} , kOe	T_{obs} , K ^a
$\text{Nb}_{(12.8 \text{ w/o})}$	15.2		>9.5		13.2
NNb (wires)	16.1		153 ^c		0
			132		4.2
			95		8
			53		12
NNb _x O _{1-x}	13.5–17.0		38		
NNb _x Zr _{1-x}	9.8–13.8		4–>130		4.2
$\text{Nb}_{0.93} \text{Nb}_{0.85} \text{Zr}_{0.15}$	13.8		>130		4.2
$\text{Na}_{0.086} \text{Pb}_{0.914}$		0.19	6.0		
$\text{Na}_{0.016} \text{Pb}_{0.984}$		0.28	2.05		
Nb	9.15		2.020		1.4
			1.710		4.2
Nb		0.4–1.1	3–5.5		4.2
Nb (unstrained)		1.1–1.8	3.40	6–9.1	4.2
Nb (strained)		1.25–1.92	3.44	6.0–8.7	4.2
Nb (cold-drawn wire)		2.48	4.10	≈10	4.2
Nb (film)			>25		4.2
NbSc			>30		
Nb_3Sn		0.170	221		4.2
			70		14.15
			54		15
			34		16
			17		17
$\text{Nb}_{0.1}\text{Ta}_{0.9}$		0.084	0.154		4.195
$\text{Nb}_{0.2}\text{Ta}_{0.8}$			10		4.2
$\text{Nb}_{0.65-0.73}\text{Ta}_{0.02-0.10}\text{Zr}_{0.25}$			>70–>90		4.2
$\text{Nb}_x\text{Ti}_{1-x}$			148 max.		1.2
			120 max.		4.2
$\text{Nb}_{0.222}\text{U}_{0.778}$		1.98	23		1.2
$\text{Nb}_x\text{Zr}_{1-x}$			127 max.		1.2
			94 max.		4.2
O_3SrTi	0.43	0.0049 ^c	0.504 ^c		0
O_3SrTi	0.33	0.00195 ^c	0.420 ^c		0
PbSb _{1 w/o} (quenched)			>1.5		4.2
PbSb _{1 w/o} (annealed)			>0.7		4.2
PbSb _{2.8 w/o} (quenched)			>2.3		4.2
PbSb _{2.8 w/o} (annealed)			>0.7		4.2
$\text{Pb}_{0.871}\text{Sn}_{0.129}$		0.45	1.1		
$\text{Pb}_{0.965}\text{Sn}_{0.035}$		0.53	0.56		
$\text{Pb}_{1-0.26}\text{Tl}_{0-0.74}$	7.20–3.68		2–6.9 ^c		0
$\text{PbTl}_{0.17}$	6.73		4.5 ^e		0
$\text{Re}_{0.26}\text{W}_{0.74}$			>30		
$\text{Sb}_{0.93}\text{Sn}_{0.07}$			0.12		3.7
SiV_3	17.0	0.55	156 ^e		
$\text{Sn}_x\text{Te}_{1-x}$		0.00043–0.00236	0.005–0.0775		0.012–0.079
Ta (99.95%)		0.425	1.850		1.3
		0.325	1.425		2.27
		0.275	1.175		2.66
		0.090	0.375		3.72
$\text{Ta}_{0.5}\text{Nb}_{0.5}$			3.55		4.2
$\text{Ta}_{0.65-0}\text{Tl}_{0.35-1}$	4.4–7.8		>14–138		1.2
$\text{Ta}_{0.5}\text{Ti}_{0.5}$			138		1.2
Te	3.3	0.25 ^c			0
$\text{Tc}_x\text{W}_{1-x}$	5.75–7.88		8–44		4.2
Ti				2.7	4.2
$\text{Ti}_{0.75}\text{V}_{0.25}$	5.3	0.029 ^c	199 ^c		0
$\text{Ti}_{0.775}\text{V}_{0.225}$	4.7	0.024 ^c	172 ^c		0
$\text{Ti}_{0.615}\text{V}_{0.385}$	7.07	0.050	34		4.2
$\text{Ti}_{0.516}\text{V}_{0.484}$	7.20	0.062	28		4.2
$\text{Ti}_{0.415}\text{V}_{0.585}$	7.49	0.078	25		4.2
$\text{Ti}_{0.12}\text{V}_{0.88}$			17.3	28.1	4.2
$\text{Ti}_{0.09}\text{V}_{0.91}$			14.3	16.4	4.2
$\text{Ti}_{0.06}\text{V}_{0.94}$			8.2	12.7	4.2

Substance	T_c , K	H_{c1} , kOe	H_{c2} , kOe	H_{c3} , kOe	T_{obs} , K ^a
$\text{Ti}_{0.03}\text{V}_{0.97}$			3.8	6.8	4.2
$\text{Ti}_x\text{V}_{1-x}$			108 max.		1.2
V	5.31	0.8	3.4		1.79
		0.75	3.15		2
		0.45	2.2		3
		0.30	1.2		4
$\text{V}_{0.26}\text{Zr}_{0.74}$	≈ 5.9	0.238			1.05
		0.227			1.78
		0.185			3.04
		0.165			3.5
W (film)	1.7–4.1		>34		1

^a Temperature of critical field measurement.^b w/o denotes weight percent.^c Extrapolated.^d Linear extrapolation.^e Parabolic extrapolation

References

- B. W. Roberts, in *Superconductive Materials and Some of Their Properties. Progress in Cryogenics*, Vol. IV, 1964, pp. 160–231.
- B. W. Roberts, Superconductive Materials and Some of Their Properties, NBS Technical Notes 408 and 482, U.S. Government Printing Office, 1966 and 1969; B. W. Roberts, *J. Phys. Chem. Ref. Data*, 5, 581, 1976.
- B. W. Roberts, Properties of Selected Superconductive Materials, 1978 Supplement, NBS Technical Note 983, 1978.
- T. Claeson, *Phys. Rev.*, 147, 340, 1966.
- C. J. Raub, W. H. Zachariasen, T. H. Geballe, and B. T. Matthias, *J. Phys. Chem. Solids*, 24, 1093, 1963.
- T. H. Geballe, B. T. Matthias, V. B. Compton, E. Corenzwit, G. W. Hull, Jr., and L. D. Longinotti, *Phys. Rev.*, 1A, 119, 1965.
- C. J. Raub, V. B. Compton, T. H. Geballe, B. T. Matthias, J. P. Maita, and G. W. Hull, Jr., *J. Phys. Chem. Solids*, 26, 2051, 1965.
- R. D. Blaughter, J. K. Hulm, and P. N. Yocom, *J. Phys. Chem. Solids*, 26, 2037, 1965.
- T. Claeson and H. L. Luo, *J. Phys. Chem. Solids*, 27, 1081, 1966.
- S. C. Ng and B. N. Brockhouse, *Solid State Comm.*, 5, 79, 1967.
- O. I. Shulishova and I. A. Shcherbak, *Izv. AN SSSR, Neorg. Materials*, 3, 1495, 1967.
- T. F. Smith and H. L. Luo, *J. Phys. Chem. Solids*, 28, 569, 1967.
- A. C. Lawson, *J. Less-Common Metals*, 23, 103, 1971.
- R. Chevrel, M. Sergent, and J. Prigent, *J. Solid State Chem.*, 3, 515, 1971.
- M. Marezio, P. D. Dernier, J. P. Remeika, and B. T. Matthias, *Mat. Res. Bull.*, 8, 657, 1973.
- J. K. Hulm and R. D. Blaughter in *Superconductivity in d- and f-Band Metals*, D. H. Douglass, Ed., American Institute of Physics, 4, 1, 1972.
- R. N. Shelton, A. C. Lawson, and D. C. Johnston, *Mat. Res. Bull.*, 10, 297, 1975.
- H. D. Wiesinger, *Phys. Status Sol.*, 41A, 465, 1977.
- O. Fischer, *Applied Phys.*, 16, 1, 1978.
- D. C. Johnston, *Solid State Comm.*, 24, 699, 1977.
- H. C. Ku and R. H. Shelton, *Mat. Res. Bull.*, 15, 1441, 1980.
- H. Barz, *Mat. Res. Bull.*, 15, 1489, 1980.
- G. P. Espinosa, A. S. Cooper, H. Barz, and J. P. Remeika, *Mat. Res. Bull.*, 15, 1635, 1980.
- E. M. Savitskii, V. V. Baron, Yu. V. Efimov, M. I. Bychkova, and L. F. Myzenkova, in *Superconducting Materials*, Plenum Press, 1981, p. 107.
- R. Fluckiger and R. Baillif, in Topics in *Current Physics*, O. Fischer and M. B. Maple, Eds., Springer Verlag, 34, 113, 1982.
- R. N. Shelton, in *Superconductivity in d- and f-Band Metals*, W. Buckel and W. Weber, Eds., Kernforschungszentrum, Karlsruhe, 1982, p. 123.
- D. C. Johnston and H. F. Braun, *Topics in Current Phys.*, 32, 11, 1982.
- R. Chevrel and M. Sergent, *Topics in Current Phys.*, 32, 25, 1982.
- G. P. Espinosa, A. S. Cooper, and H. Barz, *Mat. Res. Bull.*, 17, 963, 1982.
- R. Muller, R. N. Shelton, J. W. Richardson, Jr., and R. A. Jacobson, *J. Less-Comm. Met.*, 92, 177, 1983.
- You-Xian Zhao and Shou-An He, in *High Pressure in Science and Technology*, North Holland, 22, 51, 1983.
- You-Xian Zhao and Shou-An He, *Solid State Comm.*, 24, 699, 1983.
- G. P. Meissner and H. C. Ku, *Appl. Phys.*, A31, 201, 1983.
- R. J. Cava, D. W. Murphy, and S. M. Zahurak, *J. Electrochem. Soc.*, 130, 2345, 1983.
- R. N. Shelton, *J. Less-Comm. Met.*, 94, 69, 1983.
- B. Chevalier, P. Lejay, B. Lloret, Wang Xian-Zhong, J. Etourneau, and P. Hagenmuller, *Annales de Chemie*, 9, 191, 1984.
- G. Venturini, M. Meot-Meyer, E. McRae, J. F. Mareche, and B. Roques, *Mat. Res. Bull.*, 19, 1647, 1984.
- J. M. Tarascon, F. G. DiSalvo, D. W. Murphy, G. Hull, and J. V. Waszczak, *Phys. Rev.*, 29B, 172, 1984.
- G. V. Subba and G. Balakrishnan, *Bull. Mat. Sci.*, 6, 283, 1984.
- B. Batlogg, *Physica*, 126B, 275, 1984.
- M. J. Johnson, Ames Lab (USA) Report IS-T-1140, 1984.
- I. M. Chapnik, *J. Mat. Sci. Lett.*, 4, 370, 1985.
- W. Rong-Yao, L. Q-Guang, and Z. Xiao, *Phys. Status Sol.*, 90A, 763, 1985.
- W. Xian-Zhong, B. Chevalier, J. Etourneau, and P. Hagenmuller, *Mat. Res. Bull.*, 20, 517, 1985.
- H. R. Ott, F. Hulliger, H. Rudigier, and Z. Fisk, *Phys. Rev.*, 31B, 1329, 1985.
- P. Villars and L. D. Calver, *Pearson's Handbook of Crystallographic Data for Intermetallic Phases*, Vol. 1–3, ASM, 1985.
- G. V. Subba Rao, K. Wagner, G. Balakrishnan, J. Jakani, W. Paulus, and R. Scollhorn, *Bull. Mat. Sci.*, 7, 215, 1985.
- J. G. Bednorz and K. A. Muller, *Zs. Physik*, B64, 189, 1986.
- W. Rong-Yao, *Phys. Status Sol.*, 94A, 445, 1986.
- H. D. Yang, R. N. Shelton, and H. F. Braun, *Phys. Rev.*, 33B, 5062, 1986.
- G. Venturini, M. Kanta, E. McRae, J. F. Mareche, B. Malaman, and B. Roques, *Mat. Res. Bull.*, 21, 1203, 1986.
- W. Rong-Yao, *J. Mat. Sci. Lett.*, 5, 87, 1986.
- M. K. Wu, J. R. Ashburn, C. J. Torng, P. H. Hor, R. L. Meng, L. Gao, Z. J. Huang, Y. Q. Wang, and C. W. Chu, *Phys. Rev. Lett.*, 58, 908, 1987.
- R. J. Cava, R. B. Van Dover, B. Batlogg, and E. A. Rietman, *Phys. Rev. Lett.*, 58, 408, 1987.
- L. C. Porter, T. J. Thorn, U. Geiser, A. Umezawa, H. H. Wang, W. K. Kwok, H-C. I. Kao, M. R. Monaghan, G. W. Crabtree, K. D. Carlson, and J. M. Williams, *Inorg. Chem.*, 26, 1645, 1987.
- A. M. Kini, U. Geiser, H-C. I. Kao, K. D. Carlson, H. H. Wang, M. R. Monaghan, and K. M. Williams, *Inorg. Chem.*, 26, 1834, 1987.

57. T. Penney, S. von Molnar, D. Kaiser, F. Holtzberg, and A. W. Kleinsasser, *Phys. Rev.*, B38, 2918, 1988.
58. Y. K. Tao, J. S. Swinnea, A. Manthiram, J. S. Kim, J. B. Goodenough, and H. Steinfink, *J. Mat. Res.*, 3, 248, 1988.
59. G. G. Peterson, B. R. Weinberger, L. Lynds, and H. A. Krasinski, *J. Mat. Res.*, 3, 605, 1988.
60. J. B. Torrance, Y. Tokura, A. Nazzai, and S. S. P. Parkin, *Phys. Rev. Lett.*, 60, 542, 1988.
61. K. Kourtakis, M. Robbins, P. K. Gallagher, and T. Teifel, *J. Mat. Res.*, 4, 1289, 1989.
62. J. C. Phillips, *Physics of High- T_c Superconductors*, Academic Press, 1989, p. 336.
63. Shui Wai Lin and L. I. Berger, *Rev. Sci. Instrum.*, 60, 507, 1989.
64. M. Tinkham, *Introduction to Superconductivity*, McGraw-Hill, New York, 1975.
65. O. Fischer and M.B. Maple, Eds., *Topics in Current Physics*, Volume 32: Superconductivity in Ternary Compounds I; Volume 34: Superconductivity in Ternary Compounds II, Springer-Verlag, Berlin, 1982.
66. K. J. Dunn and F. P. Bundy, *Phys. Rev.*, B25, 194, 1982.
67. A. Barone and G. Paterno, *Physics and Applications of the Josephson Effect*, Wiley, New York, 1982.
68. D. H. Douglass, Ed., *Superconductivity in d- and f-Band Metals*, Plenum Press, New York, 1976.
69. D. M. Ginsberg, Ed., *Physical Properties of High Temperature Superconductors*, (Volume II, 1990; Volume III, 1992; Volume V, 1996), World Scientific, Singapore.
70. T. Ishiguro and K. Yamji, *Organic Superconductors*, Springer-Verlag, Berlin, 1990.
71. Sh. Okada, K. Shimizu, T. C. Kobayashi, K. Amaya, and Sh. Endo, *J. Phys. Soc. Jpn.*, 65, 1924, 1996.
72. A. Bourdillon and N. X. Tan Bourdillon, *High Temperature Superconductors: Processing and Science*, Academic Press, 1994.
73. J. M. Williams, J. R. Ferraro, R. J. Thorn, K. Carlson, U. Geiser, H. H. Wang, A. M. Kini, and M.-H. Whangbo, *Organic Superconductors (Including Fullerenes): Synthesis, Structure, Properties, and Theory*, Prentice-Hall, 1992.
74. J. Nagamatsu, N. Nakagawa, T. Muranaka, Y. Zenitani, and J. Akimitsu, *Nature (London)*, 410, 63, 2001.
75. Y. Boguslavsky, G. K. Perkins, X. Qi, L. F. Cohen, and A. D. Caplin, *Nature (London)*, 410, 563, 2001.
76. B. Q. Fu, Y. Feng, G. Yan, Y. Zhao, A. K. Pradhan, C. H. Cheng, P. Ji, X. H. Liu, C. F. Liu, L. Zhou, and K. F. Yau, *J. Appl. Phys.*, 92, 7341, 2002.